

SVENSK STANDARD

SS-EN 16140:2019



Fastställt/Approved: 2019-01-28
Utgåva/Edition: 2
Språk/Language: engelska/English
ICS: 91.100.15

Provningsmetoder för natursten – Bestämning av estetiska förändringar genom värmepåverkan

Natural stone test methods – Determination of sensitivity to changes in appearance produced by thermal cycles

This preview is downloaded from www.sis.se. Buy the entire standard via <https://www.sis.se/std-80009467>

Standarder får världen att fungera

SIS (Swedish Standards Institute) är en fristående ideell förening med medlemmar från både privat och offentlig sektor. Vi är en del av det europeiska och globala nätverk som utarbetar internationella standarder. Standarder är dokumenterad kunskap utvecklad av framstående aktörer inom industri, näringsliv och samhälle och befrämjar handel över gränser, bidrar till att processer och produkter blir säkrare samt effektiviserar din verksamhet.

Delta och påverka

Som medlem i SIS har du möjlighet att påverka framtida standarder inom ditt område på nationell, europeisk och global nivå. Du får samtidigt tillgång till tidig information om utvecklingen inom din bransch.

Ta del av det färdiga arbetet

Vi erbjuder våra kunder allt som rör standarder och deras tillämpning. Hos oss kan du köpa alla publikationer du behöver – allt från enskilda standarder, tekniska rapporter och standardpaket till handböcker och onlinetjänster. Genom vår webbtjänst e-nav får du tillgång till ett lättnavigerat bibliotek där alla standarder som är aktuella för ditt företag finns tillgängliga. Standarder och handböcker är källor till kunskap. Vi säljer dem.

Utveckla din kompetens och lyckas bättre i ditt arbete

Hos SIS kan du gå öppna eller företagsinterna utbildningar kring innehåll och tillämpning av standarder. Genom vår närhet till den internationella utvecklingen och ISO får du rätt kunskap i rätt tid, direkt från källan. Med vår kunskap om standarders möjligheter hjälper vi våra kunder att skapa verklig nytta och lönsamhet i sina verksamheter.

Vill du veta mer om SIS eller hur standarder kan effektivisera din verksamhet är du välkommen in på www.sis.se eller ta kontakt med oss på tel 08-555 523 00.



Standards make the world go round

SIS (Swedish Standards Institute) is an independent non-profit organisation with members from both the private and public sectors. We are part of the European and global network that draws up international standards. Standards consist of documented knowledge developed by prominent actors within the industry, business world and society. They promote cross-border trade, they help to make processes and products safer and they streamline your organisation.

Take part and have influence

As a member of SIS you will have the possibility to participate in standardization activities on national, European and global level. The membership in SIS will give you the opportunity to influence future standards and gain access to early stage information about developments within your field.

Get to know the finished work

We offer our customers everything in connection with standards and their application. You can purchase all the publications you need from us - everything from individual standards, technical reports and standard packages through to manuals and online services. Our web service e-nav gives you access to an easy-to-navigate library where all standards that are relevant to your company are available. Standards and manuals are sources of knowledge. We sell them.

Increase understanding and improve perception

With SIS you can undergo either shared or in-house training in the content and application of standards. Thanks to our proximity to international development and ISO you receive the right knowledge at the right time, direct from the source. With our knowledge about the potential of standards, we assist our customers in creating tangible benefit and profitability in their organisations.

If you want to know more about SIS, or how standards can streamline your organisation, please visit www.sis.se or contact us on phone +46 (0)8-555 523 00



Europastandarden EN 16140:2019 gäller som svensk standard. Detta dokument innehåller den officiella engelska versionen av EN 16140:2019.

Denna standard ersätter SS-EN 16140:2011, utgåva 1.

The European Standard EN 16140:2019 has the status of a Swedish Standard. This document contains the official version of EN 16140:2019.

This standard supersedes the SS-EN 16140:2011, edition 1.

© Copyright/Upphovsrätten till denna produkt tillhör SIS, Swedish Standards Institute, Stockholm, Sverige. Användningen av denna produkt regleras av slutanvändarlicensen som återfinns i denna produkt, se standardens sista sidor.

© Copyright SIS, Swedish Standards Institute, Stockholm, Sweden. All rights reserved. The use of this product is governed by the end-user licence for this product. You will find the licence in the end of this document.

Upplysningar om sakinnehållet i standarden lämnas av SIS, Swedish Standards Institute, telefon 08-555 520 00. Standarder kan beställas hos SIS som även lämnar allmänna upplysningar om svensk och utländsk standard.

Information about the content of the standard is available from the Swedish Standards Institute (SIS), telephone +46 8 555 520 00. Standards may be ordered from SIS, who can also provide general information about Swedish and foreign standards.

Denna standard är framtagen av kommittén för Natursten, SIS/TK 508.

Har du synpunkter på innehållet i den här standarden, vill du delta i ett kommande revideringsarbete eller vara med och ta fram andra standarder inom området? Gå in på www.sis.se - där hittar du mer information.

EUROPEAN STANDARD

EN 16140

NORME EUROPÉENNE

EUROPÄISCHE NORM

January 2019

ICS 91.100.15

Supersedes EN 16140:2011

English Version

Natural stone test methods - Determination of sensitivity to changes in appearance produced by thermal cycles

Méthodes d'essai pour pierres naturelles -
Détermination de la sensibilité aux changements
d'aspect induits par des cycles thermiques

Prüfverfahren für Naturwerkstein - Bestimmung der
Empfindlichkeit gegen Änderungen des äußeren
Erscheinungsbildes durch thermische Zyklen

This European Standard was approved by CEN on 19 November 2018.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Rue de la Science 23, B-1040 Brussels

SS-EN 16140:2019 (E)

Contents		Page
European foreword		3
1	Scope	5
2	Normative references	5
3	Terms and definitions	5
4	Symbols and abbreviations	5
5	Principle	5
6	Apparatus	5
7	Preparation of specimens	5
7.1	Sampling	5
7.2	Test specimens	6
7.2.1	Surface finish	6
7.2.2	Dimensions	6
8	Test procedures	6
8.1	Control measurements before cycling	6
8.2	Description of the cycles	6
8.3	Control measurements after cycling	6
9	Expression of results	9
10	Test report	9
Annex A (informative) Examples of evaluation codes for changes of aspect		11
Annex B (informative) Adapted thermal shock test		17

European foreword

This document (EN 16140:2019) has been prepared by Technical Committee CEN/TC 246 “Natural stones”, the secretariat of which is held by UNI.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by July 2019, and conflicting national standards shall be withdrawn at the latest by July 2019.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN shall not be held responsible for identifying any or all such patent rights.

This document will supersede EN 16140:2011.

In comparison with the previous edition, the changes concern essentially the interpretation of the modification of aspect after the thermal cycles.

In Annex A, the figures are completed and clarified.

This European Standard is one of the series of standards for tests on natural stone.

Test methods for natural stone consist of the following standards:

- EN 1925, *Natural stone test methods — Determination of water absorption coefficient by capillarity;*
- EN 1926, *Natural stone test methods — Determination of uniaxial compressive strength;*
- EN 1936, *Natural stone test methods — Determination of real density and apparent density, and of total and open porosity;*
- EN 12370, *Natural stone test methods — Determination of resistance to salt crystallization;*
- EN 12371, *Natural stone test methods — Determination of frost resistance;*
- EN 12372, *Natural stone test methods — Determination of flexural strength under concentrated load;*
- EN 12407, *Natural stone test methods — Petrographic examination;*
- EN 12440, *Natural stone — Denomination criteria;*
- EN 12670, *Natural stone — Terminology;*
- EN 13161, *Natural stone test methods — Determination of flexural strength under constant moment;*
- EN 13364, *Natural stone test methods — Determination of the breaking load at dowel hole;*
- EN 13373, *Natural stone test methods — Determination of geometric characteristics on units;*
- EN 13755, *Natural stone test methods — Determination of water absorption at atmospheric pressure;*
- EN 14066, *Natural stone test methods — Determination of resistance to ageing by thermal shock;*
- EN 14146, *Natural stone test methods — Determination of the dynamic modulus of elasticity (by measuring the fundamental resonance frequency);*

SS-EN 16140:2019 (E)

- EN 14147, *Natural stone test methods — Determination of resistance to ageing by salt mist;*
- EN 14157, *Natural stone test methods — Determination of the abrasion resistance;*
- EN 14158, *Natural stone test methods — Determination of rupture energy;*
- EN 14231, *Natural stone test methods — Determination of the slip resistance by means of the pendulum tester;*
- EN 14579, *Natural stone test methods — Determination of sound speed propagation;*
- EN 14580, *Natural stone test methods — Determination of static elastic modulus;*
- EN 14581, *Natural stone test methods — Determination of linear thermal expansion coefficient;*
- EN 16301, *Natural stone test methods — Determination of sensitivity to accidental staining.*

According to the CEN-CENELEC Internal Regulations, the national standards organisations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

1 Scope

This document specifies a method to assess possible alterations of natural stones (mainly visible sensitivity to oxidation processes) under the effect of sudden changes in temperature (thermal shock).

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN ISO 11664-2, *Colorimetry - Part 2: CIE standard illuminants (ISO 11664-2)*

3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

4 Symbols and abbreviations

e Thickness of the test specimens, in mm

5 Principle

The specimens are subjected to successive cycles, each formed by drying at (70 ± 5) °C followed by immediate immersion in water at (20 ± 5) °C.

6 Apparatus

- 6.1 A ventilated oven capable of maintaining a temperature of (70 ± 5) °C.
- 6.2 A covered tank with a flat base, comprising small non-oxidising and non-absorbent supports for the specimens.
- 6.3 A digital camera of a minimum 2,5 MPixels, uncompressed or a scanner, with a sufficient resolution.
- 6.4 Daylight or artificial light D65 (6 500 K) according to EN ISO 11664-2.
- 6.5 A magnifying glass of at least five increases.

7 Preparation of specimens

7.1 Sampling

The sampling is not the responsibility of the test laboratory except where specially requested. At least seven specimens shall be selected from a homogeneous batch. One of these specimens is used as reference specimen and is not subjected to any tests.

The samples shall be representative of the stone and avoid irrelevant particularities.

SS-EN 16140:2019 (E)

7.2 Test specimens

7.2.1 Surface finish

As a standard reference (identification test) surface finish of the faces of the specimens shall be sawn.

In case of necessity as required for application (technological test), other surface finishes (e.g. honed, polished, flamed, sandblasted, splitting) may be tested.

7.2.2 Dimensions

As a standard reference (identification test) the test specimens shall be $(200 \times 200) \text{ mm} \pm 10 \text{ mm} \times e$.

In case of necessity as required for application (technological test), other dimensions may be used. In this case, test specimens may be final products or sawn from final products.

8 Test procedures

8.1 Control measurements before cycling

The standardized surfaces of dried specimens are submitted to a thorough visual inspection, with the aid of a magnifying glass of at least five increases. All relevant features of its texture and also all visual and structural alterations of each specimen shall be noted, such as cracks, holes, swelling, spots, oxidations, or presence of metallic minerals or other sensitive minerals (e.g. biotite, hornblendes, etc.). A photographic (or scanner) record of all specimens to be tested shall be made. Daylight or artificial light D65 is used during the photography and the evaluation.

8.2 Description of the cycles


As a standard reference (identification test) the specimens are subjected to changes of temperature according to the following procedure: $(18 \pm 1) \text{ h}$ in a ventilated oven at $(70 \pm 5) \text{ }^\circ\text{C}$, immediately followed by $(6 \pm 0,5) \text{ h}$ of complete submersion in distilled or demineralized water, whose temperature before the immersion of the specimens is $(20 \pm 5) \text{ }^\circ\text{C}$.

Both in the oven and in the water container, the specimens are placed in vertical position on the supports at a distance of at least 50 mm from one another and from the wall. In the water container, the specimens are placed on supports located at the bottom of the container which has been filled with water to such a height that its level above the specimens is $(60 \pm 10) \text{ mm}$. The procedure described above constitutes one cycle. If the test is to be interrupted at any time, other than for testing, then the specimens are to be immersed in water at $(20 \pm 5) \text{ }^\circ\text{C}$. The test consists in a total of 20 cycles.

8.3 Control measurements after cycling

After the 20th cycle, the standardized surfaces of the specimens are visually inspected and compared general aspect or colour with the reference specimen. All alterations are noted. A photographic (or scanner) record shall be made, which includes both tested specimens and reference specimen placed next to one another.

The observation shall be carried out by placing the reference specimen against the tested specimens and viewing them at a distance of about two metres under normal daylight conditions and recording any visible differences in the characteristics of the stones (see Figure 1).

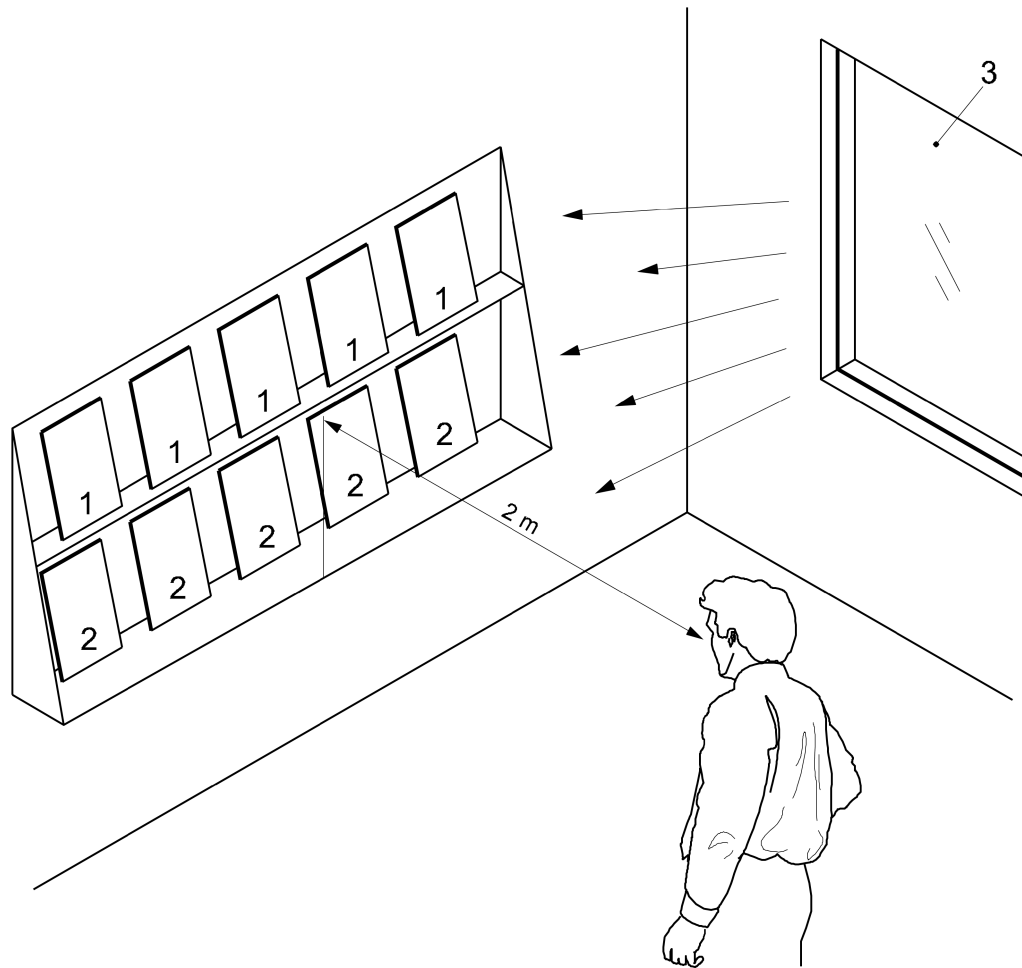

Key

- 1 reference specimen
- 2 tested specimen
- 3 daylight

Figure 1 — Comparison between tested specimens and reference specimen

Only noticeable changes visible are to be taken into account if they reach more than 1 % of the surface of the specimen. If visible changes are typical or accepted for the tested stone and as its technical performances are not adversely affected, they are permitted.

The concentration of any observed change shall be accurately identified and expressed: mean dimension/diameter of the occurrence, percentage of the affected surface. The percentage shall be given according to Figure 2.